

Cordage Institute – Dave Richards

15K TEST FRAME WITH 1" DIA. PIN & BOLLARD

Method

This type of testing is to determine the percentage of the knot strength vs. rope strength. The first step is to determine the average of each type rope with five breaks in accordance with CI-1801. The ropes were tested and the mean and standard deviation was determined. Each of the knots was tested and the break strength recorded. The Bowline, Fig. 8 end and bight, and the Butterfly knot had one end on the bollard. Bollards on both ends held the Fisherman's, and Sheet Bend knots. The mean and standard deviation were determined. This was then compared to break strength of the rope and percent of break strength determined. In all testing there is some variation, to eliminate as much of this as possible all the knots were tied by the same person using the same procedures. The data was then recorded on Excel and the various graphs and charts were compiled.

Data

Normally there are three categories referring to types of configurations in the end or joining of rope. Knots, Bends, and Hitches. However for simplicity and clarity in this paper we will divide this data into two categories; End line knots and joining knots. The Bowline, Figure 8 end and bight, and Butterfly are end line knots that are to hold on to something. Sheet Bend and Fisherman's Knot are to joining two ropes of the same size and type together. To determine the consistency we used the Standard Deviation divided into the mean break strength. Standard Deviation is the square root of (the sum of the squared deviations from the mean, divided by the sample size minus one) In formulae it is often represented by the letters SD or the symbol (Greek letter) sigma. The lower the percentage the more consistent the knot. It was necessary to add backup knots, as noted, to get the rope to break.

12.5 mm Static Life Safety Rope Data

	Brk. Str.	Bowline	Fig. 8 end	Fig. 8 bight	Butterfly	Sheet Bend	Fish knot	Dbl Sheet Bnd	Dbl Fish Knot
Brk 1	10,102.0	6,414.0	7,299.0	7,798.0	8,028.0	5,219.0	5,149.0	5,440.0	7,756.0
Brk 2	9,984.0	6,240.0	7,548.0	7,562.0	8,078.0	4,962.0	5,515.0	5,372.0	7,705.0
Brk 3	9,967.0	6,271.0	7,641.0	7,536.0	8,069.0	5,065.0	5,371.0	5,402.0	7,818.0
Brk 4	9,773.0	6,170.0	7,446.0	7,773.0	8,069.0	5,175.0	5,195.0	5,585.0	7,749.0
Brk 5	9,820.0	6,315.0	7,453.0	7,788.0	7,779.0	4,984.0	5,147.0	5,363.0	7,800.0
Mean	9,929.2	6,282.0	7,477.4	7,691.4	8,004.6	5,081.0	5,275	5,432.4	7,765.6
Std. Dev.	132.9	90.7	127.6	130.6	127.6	113.7	162.4	90.5	44.6
% Of Brk	100%	63.3%	75.3%	77.5%	80.6%	51.1%	53.1%	54.7%	78.2%
% Of Brk	1.3%	1.4%	1.7%	1.7%	1.6%	2.2%	3.0%	1.7%	0.05%

Note: Fish Knot has a tendency to slip @4400 lbs. without 2 half hitches on both sides

Note: Double Sheet Bend pulled out at 3,705 lbs. included a an Overhand knot on bend back side to achieve breaks.

Fig. 1

10.5 mm Dynamic Climbing Rope Data

	Brk. Str.	Bowline	Fig. 8 end	Fig. 8 bight	Butterfly	Sheet Bend	Fish knot	Dbl Sheet Bnd	Dbl Fish Knot
Brk 1	4,994.0	3,112.0	3,289.0	3,492.0	3,544.0	2,576.0	3,109.0	2,632.0	3,445.0
Brk 2	4,963.0	3,051.0	3,633.0	3,643.0	3,407.0	2,575.0	3,000.0	2,795.0	3,727.0
Brk 3	4,959.0	3,223.0	3,470.0	3,507.0	3,663.0	2,520.0	2,946.0	2,873.0	3,640.0
Brk 4	5,250.0	3,233.0	3,489.0	3,535.0	3,519.0	2,427.0	3,066.0	2,712.0	3,925.0
Brk 5	5,015.0	3,276.0	3,588.0	3,440.0	3,688.0	2,483.0	3,064.0	2,734.0	3,766.0
Mean	5,036.2	3,179.0	3,493.8	3,523.4	3,564.2	2,516.2	3,037.0	2,749.2	3,700.6
Std. Dev.	121.7	93.7	133.0	75.2	114.3	63.4	64.0	90.5	176.3
% of Brk	100%	63.1%	69.4%	69.9%	70.8%	49.9%	60.3%	54.6%	73.4%
% of Brk	2.4%	2.9%	3.8%	2.1%	3.2%	2.5%	2.1%	3.3%	4.7%

Note: Sheet Bend slips without 2 half hitches on the bend back line and overhand knot on turn thru line. With 8" tail pulled to 912 lbs. resulting in 4" tails @ 1600 lbs. the knot pulled out. Recommend always taking half hitches and overhand knot.

Fig. 2

7 mm Accessory Cord Data

	Brk. Str.	Bowline	Fig. 8 end	Fig. 8 bight	Butterfly	Sheet Bend	Fish knot	Dbl Sheet Bnd	Dbl Fish Knot
Brk 1	2,433.0	1,620.0	1,851.0	1,816.0	1,739.0	1,521.0	1,480.0	1,477.0	1,985.0
Brk 2	2,420.0	1,704.0	1,794.0	1,815.0	1,799.0	1,420.0	1,445.0	1,355.0	1,949.0
Brk 3	2,468.0	1,600.0	1,792.0	1,899.0	1,754.0	1,521.0	1,430.0	1,332.0	2,015.0
Brk 4	2,455.0	1,694.0	1,790.0	1,799.0	1,739.0	1,443.0	1,487.0	1,489.0	1,927.0
Brk 5	2,460.0	1,597.0	1,742.0	1,819.0	1,785.0	1,568.0	1,466.0	1,357.0	2,041.0
Mean	2,447.2	1,643.0	1,793.8	1,829.6	1,763.2	1,494.6	1,461.6	1,402.0	1,983.4
Std. Dev.	19.9	52.0	38.6	39.5	27.4	61.3	23.9	74.7	46.6
% of Brk	100.0%	67.1%	73.3%	74.7%	72.0%	61.1%	59.7%	57%	81.0%
% of Brk	0.08%	3.2%	2.2%	2.1%	1.6%	4.1%	1.6%	5.3%	2.3%

NOTE 1: Sheet Bend with back up knots 2 half hitches on bend back side and overhand knot on pass thru side.

NOTE 2: Double Sheet bend had a lot of slipping 4 of 5 knots broke cover first - Double Sheet Bend with 2 half hitches on bend back side broke same as Note 1

Fig. 3

Comparison Charts

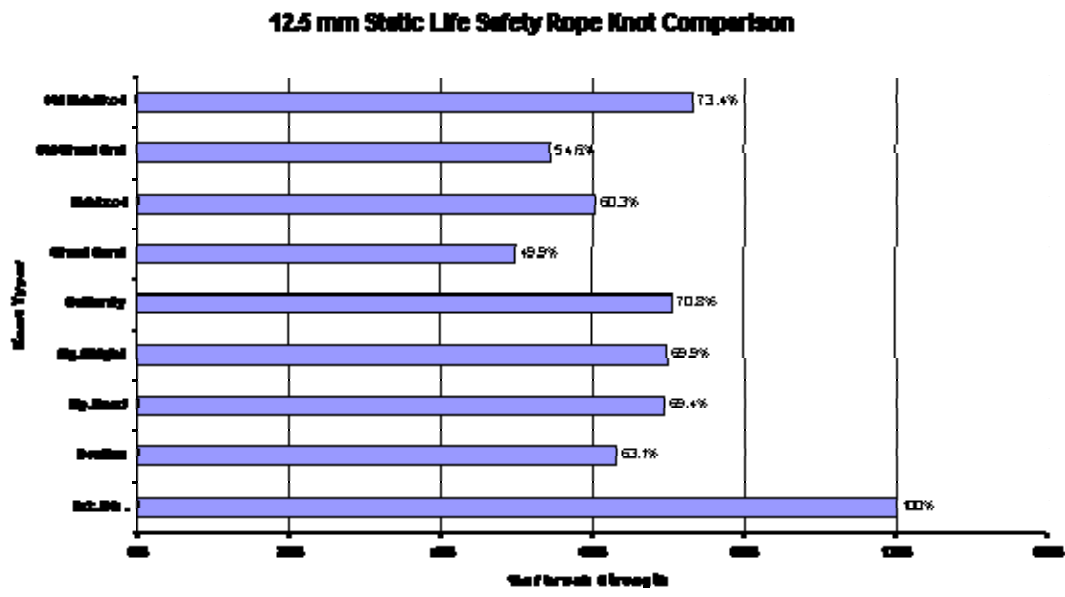


Fig. 4

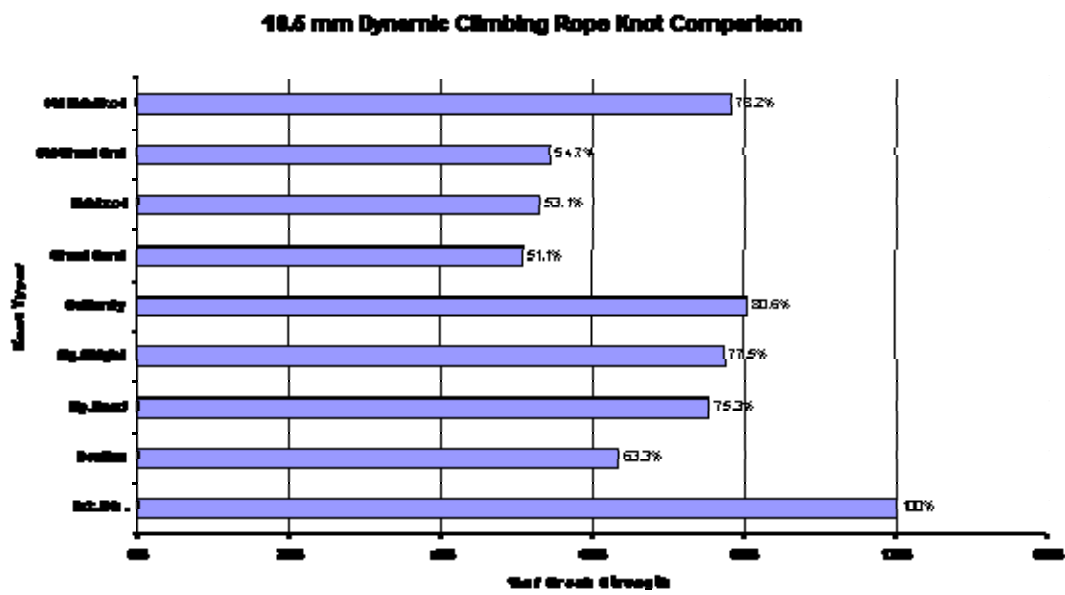


Fig. 5

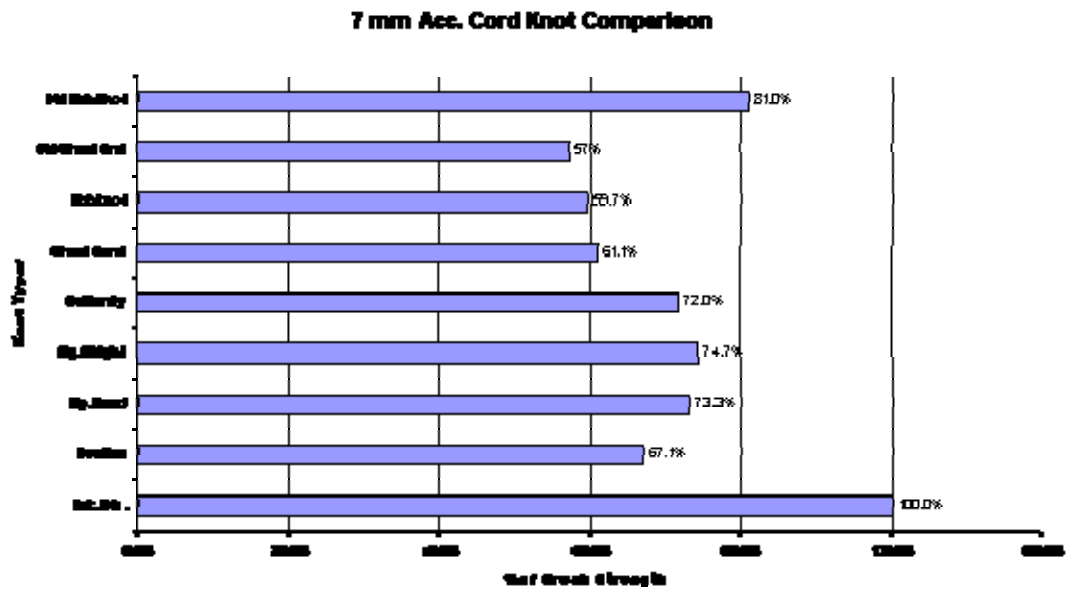


Fig. 6

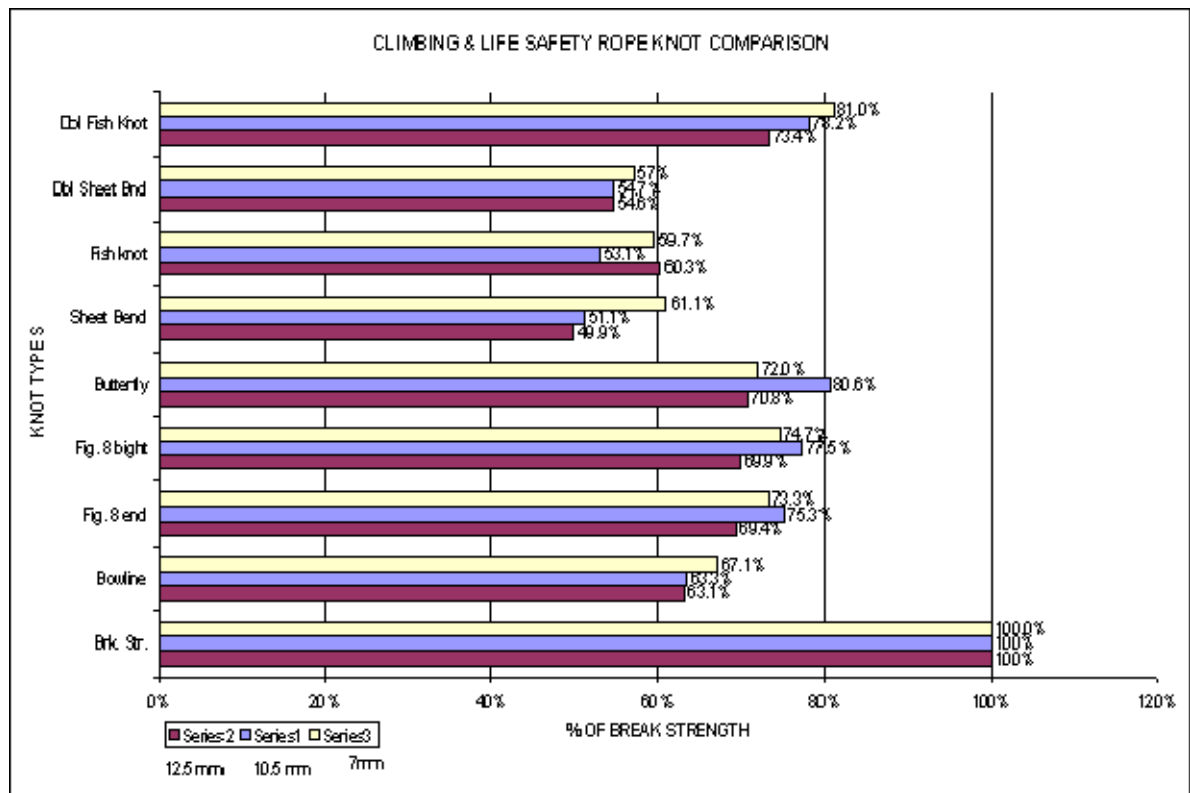


Fig. 7

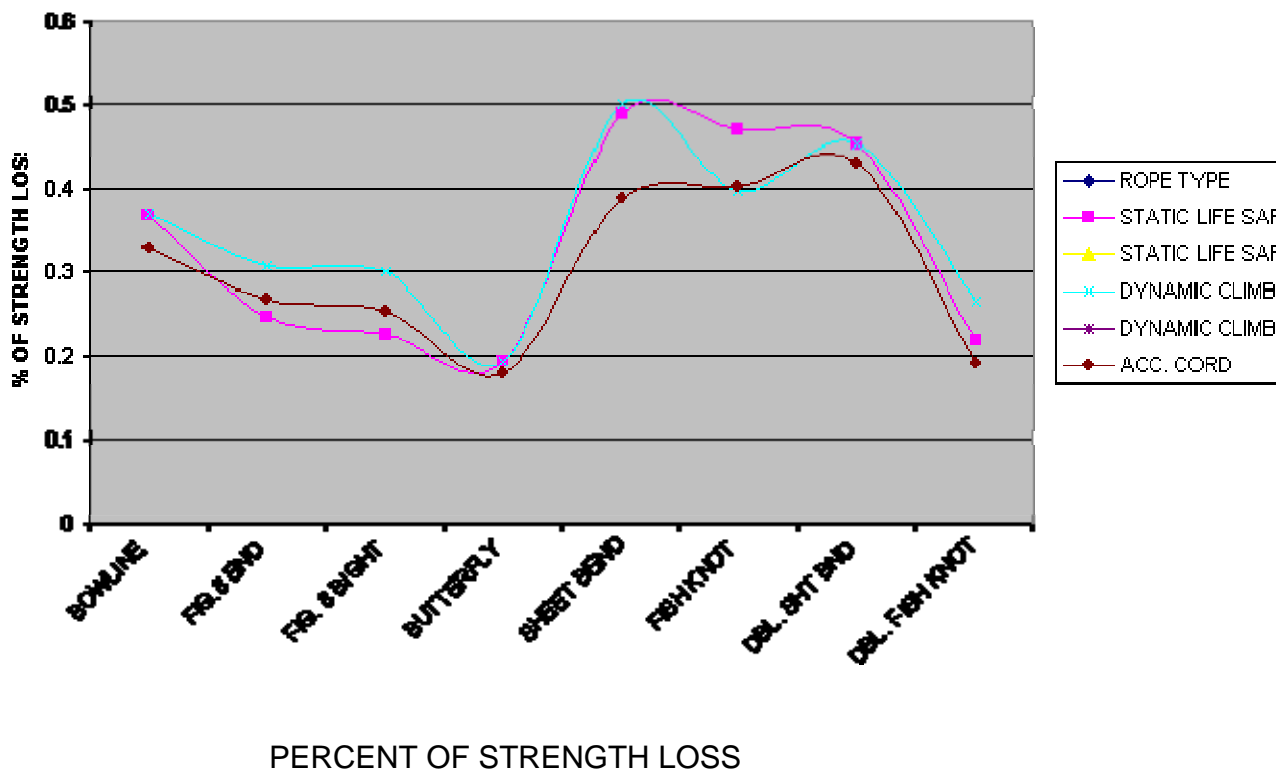


Fig. 8

Comments

The answer to the question of strength loss is "it depends". In the testing process it was very obvious that it was important to tie the knot carefully, paying attention to detail. By observing the knot tighten down any malfunction became very obvious quickly and resulted in low break strength or a pull out. The joining knots seemed to be the most susceptible. The speed of the ram used was 39"/min., faster or slower speeds may result in slightly different values. It was also found that size and material have a minor influence on the efficiency of the knot. A Bowline in the 2 larger sizes 12.5mm Static and 10.5mm Dynamic were almost the same, 7mm Acc. Cord was approximately 4% higher. The Figure 8 knots were slightly more efficient with the 10.5mm a little better than the 7mm with the 12.5mm the least. A Butterfly knot had the highest efficiency in the 10.5mm at over 80%. The Double Fisherman's Knot seemed to be the best joining knot. Most all of the joining knots required backup knots.

The most efficient end line knots Butterfly and Figure 8 knots have a disadvantage of being almost impossible to untie after a significant load of about 1,000 lbs. was applied.

The standard Bowline was selected for the test, but the Cowboy or Dutch Bowline was tested to see if there was a difference. The numbers were almost identical.

There are many other knots and variations of knots that could be tested. It has also been suggested that pre-cycling the knots to a lower load prior to break may have an effect. As stated in the beginning this is a work in progress and may never be complete.